






Score Lines on Ceramic Anilox Rolls

Shiny lines around the circumference of an anilox roll are an indication of localized wear (scoring), or deposits of foreign material in the engraved cells. The lines are usually very narrow and appear as one or more reflective bands across a roll surface. Sometimes, but not always, the bands will show up in print - particularly during heavy ink laydown.

If a doctor blade fragment, or another piece of hard foreign material, becomes trapped under the doctor blade and held against the engraved ceramic surface of the roll, it can polish that point completely around the roll until it disintegrates. The polished band that is created will release ink differently than the cells adjacent to it. The hard material may be a small fragment of the ceramic coating material itself chipped from the roll surface during handling, or it may have originated from agglomerated ink particles native to the ink in use - hard constituents such as titanium dioxide (TiO₂) may be found in ink formulations.

A more common cause of shiny line formation is the deposition of softer material in the cells and lands of the engraved anilox surface. If a material softer than the chromium oxide coating on the roll is held against the roll surface, it may deposit fragments of itself in the ink-holding cells, or the surface lands between the cells, until nothing remains. The band of cells around the roll that is affected may again have different ink release characteristics than the remainder of the roll.

Material from the doctor blade itself is the most common villain in this scenario, and doctor blade chambers that utilize containment blades exhibit a greater tendency toward trapping particles - probably because there are more surfaces available to do so. Metal or plastic doctor blade material may be trapped between a blade and the engraving, become heated from friction, and imbed itself in the roll surface. Some plastic blades seem to be more susceptible to trapping foreign material because of their softer characteristics. Since it is not usually possible to notice the formation of this kind of anilox roll damage immediately, prevention is the best remedy.

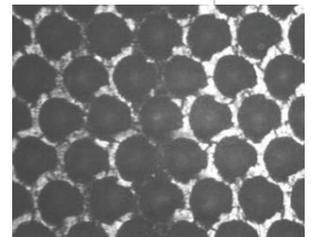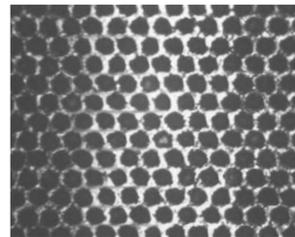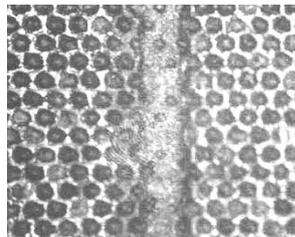

Prevention Techniques

The steps necessary to prevent shiny lines from forming start with the inking system itself and involve good doctoring and maintenance practices.

Magnets - Be certain the ink fountain or pot contains magnets to capture metal fragments in the inking system. The placement of these magnets depends upon the type of system: in circulating systems, position them in, or near, the return loop to capture particles before they can be sent back to the roll; in an open fountain, place the magnets strategically in the fountain to cover the greatest area.

Filters - The addition of filters to closed-loop inking systems with pump circulation can trap foreign materials of any type. The size of particles removed is limited only by the mesh of the filter itself. Filters can remove fragments of doctor blades made of any material, agglomerated ink particles, and any other foreign material that may find its way into the ink system. As with any filtered system, regular maintenance of the ink system filters is required to remove accumulated particles and ensure full system flow.

Blades - Doctor blades are intended to wipe the surface of an anilox roll, not force more ink into it. Once a blade is

in contact with the surface, additional blade pressure simply bends the blade, increasing wear and creating heat from increased friction.

A good rule of thumb for doctor blade pressure is 1/2 oz. per inch of blade length. The edge of the blade does the doctoring, so ensure the edge is clean and sharp, not worn or damaged. Above all, keep any blade maintenance operation clean, to prevent the inadvertent introduction of foreign material to the inking system that may damage the anilox roll engraving.

Surface Finish - Enhancing the smoothness of the surface of an anilox roll reduces friction. This, in turn, reduces doctor blade wear and prevents the formation of shiny lines. Additional superfinishing is recommended, in some cases, when specifying anilox rolls, and Praxair Surface Technologies can help determine when this may be appropriate. A normal laser engraving process results in small peaks of material around engraved cells that are removed by this process, making the surface smoother for mating blades.

A new breakthrough technology, the Novaline™ Engravings, developed by and only available from Praxair Surface Technologies, provides a smooth, level, roll surface with minimal superfinishing. This process improves the density and lowers the recast surrounding each engraved cell, provides more effective doctoring, and promises more consistent ink delivery.

How to Get Started. Contact Us Today.

Ask a Praxair printing specialist to recommend the best engraving for your application.

Call the nearest location or send us an e-mail at printing_sales@praxair.com.

www.praxair.com/printing

Brazil
Pinhais
+55 (41) 3661 6200

China
Changzhou
+86 5198622 1778

Italy
Novara
+39 0321 674811

Japan
Kozuki
+81 79088 0564

Switzerland
Meyrin
+41 22 989 8989

United Kingdom
Swindon
+44 (1) 793 512 555

United States
Charlotte, NC
+1 704 921 5400

External Factors to be Checked:

Inking System:

- Magnets
- Filters

Doctor Chamber:

- Parallelism
- Overpressure
- End blades hang outside the roll
- Dust under the blade and the roll
- Blade:
 - Pressure
 - Overwear of the blade
 - Maintenance
 - Blade material (Steel, Plastic, Ceramic)

Press set-up:

- Never run the press dry

Anilox:

- Cleaning
- Maintenance
- Storage
- Anilox Surface



© Copyright 2011 Praxair Technology, Inc.
All rights reserved

Praxair and the Flowing Airstream design are trademarks of Praxair Technology, Inc. in the United States and/or other countries.

The information contained herein is offered for use by technically qualified personnel at their discretion and risk without warranty of any kind.

Praxair Surface Technologies, Inc.
1500 Polco Street
Indianapolis, IN 46222

www.praxairsurfacetechologies.com
psti-info@praxair.com

Printed in the United States of America
09-2011

Printed on recycled paper
P-9122

Telephone:
+1 317 240 2500

Fax:
+1 317 240 2255